


This article was downloaded by: [Mantanis, George I.]

On: 10 June 2010

Access details: Access Details: [subscription number 915964543]

Publisher Taylor & Francis

Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK

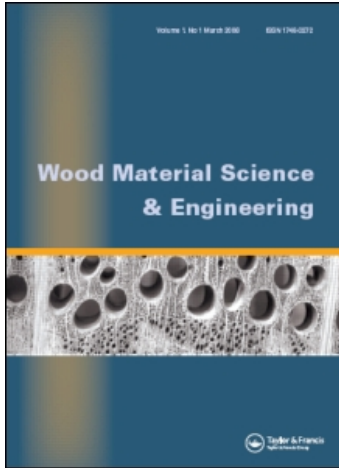

Wood Material Science and Engineering

Publication details, including instructions for authors and subscription information:

<http://www.informaworld.com/smpp/title~content=t741771155>

Physical and mechanical properties of *Pinus leucodermis* wood

George Mantanis^a; Stergios Adamopoulos^b; Ekaterina Rammou^a

^a Laboratory of Wood Technology, Department of Wood & Furniture Design and Technology, ^b

Department of Forestry and Management of Natural Environment, Technological Education Institute of Larissa, Karditsa, Greece

Online publication date: 10 June 2010

To cite this Article Mantanis, George , Adamopoulos, Stergios and Rammou, Ekaterina(2010) 'Physical and mechanical properties of *Pinus leucodermis* wood', Wood Material Science and Engineering, 5: 1, 50 – 52

To link to this Article: DOI: 10.1080/17480270903582197

URL: <http://dx.doi.org/10.1080/17480270903582197>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.informaworld.com/terms-and-conditions-of-access.pdf>

This article may be used for research, teaching and private study purposes. Any substantial or systematic reproduction, re-distribution, re-selling, loan or sub-licensing, systematic supply or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

SHORT NOTE

Physical and mechanical properties of *Pinus leucodermis* woodGEORGE MANTANIS¹, STERGIOS ADAMOPOULOS² & EKATERINA RAMMOU¹¹Laboratory of Wood Technology, Department of Wood & Furniture Design and Technology, and ²Department of Forestry and Management of Natural Environment, Technological Education Institute of Larissa, GR-431 00, Karditsa, Greece**Abstract**

The present work reports on the main physical and mechanical properties of *Pinus leucodermis* mature wood, one of the least studied coniferous species in south-east Europe. *Pinus leucodermis* heartwood specimens were found to have average density values of 0.73 g cm^{-3} at equilibrium moisture content of 11.5% and average density of 0.64 g cm^{-3} under oven-dry conditions. The overall tangential shrinkage was 3.4% and the radial shrinkage was 1.9%. The modulus of rupture was on average 77 N mm^{-2} , while the static modulus of elasticity averaged 7087 N mm^{-2} . The hardness of *P. leucodermis* heartwood using the modified Janka test was 33.4 N mm^{-2} in the transverse direction and 48.0 N mm^{-2} in the longitudinal direction, while its compression strength parallel to grain was approximately 41.6 N mm^{-2} .

Keywords: *Bosnian pine, heartwood, Pinus leucodermis wood.*

Introduction

Pinus leucodermis, also known as Bosnian pine, is a forest species that occurs in the mountains of south-eastern Europe, in south-western Bulgaria, Bosnia, Albania, the former Yugoslav Republic of Macedonia, Serbia, northern Greece and locally in the south of Italy, growing at altitudes of 900–2500 m. It is a slow-growing species that usually grows up to a height of 38–40 m and a diameter of 150 cm (Farjon, 2005).

The species is mainly an ornamental and landscape tree rather than a timber crop. *Pinus leucodermis* wood is typically used in Greece and other areas in round form for building poles and fences and as raw material for making excellent wine barrels (Tsoumis, 1991). *Pinus leucodermis* wood has numerous resin canals (Figure 1) in the cross-section and is also characterized by a very distinctive resin odour. In recent years, there has been commercial interest in *P. leucodermis* wood for other technical uses (e.g. construction, window frames). However, information on the physical and mechanical properties of this timber, which is a prerequisite to enhance its uses, is very limited in the literature.

Materials and methods

Straight-grained mature heartwood of *P. leucodermis*, with an average number of 6–8 annual rings cm^{-2} , was collected from a high-altitude forest area of Pindos in north-west Greece. After a slow air-drying process of 6 months, small, clear wood specimens



Figure 1. Cross-section of *Pinus leucodermis* wood with numerous resin canals.

Table I. Information on testing of *Pinus leucodermis* wood.

Property	No. of specimens	Dimensions of specimens ^a	Standard
Density	40	40 × 20 × 20	DIN 52182
Shrinkage and swelling	30	10 × 20 × 20	DIN 52184
Static bending	40	360 × 20 × 20	DIN 52186
Axial compression	40	60 × 20 × 20	DIN 52185
Hardness (Janka)	20	50 × 50 × 50	ASTM D143-94

Note: ^alongitudinal × radial × tangential (mm × mm × mm).

were prepared from this material according to Table I. The specimens were then conditioned under normal conditions (20°C, 65 ± 3% relative humidity) for 8 weeks.

Wood density was determined according to DIN 52182 standards under two conditions: oven-dry and at 20°C and 65 ± 3% relative humidity. Shrinkage and swelling values (radial, tangential) were based on the measurement of the dimensions of the specimens under green and oven-dry conditions in accordance with the standard methodology (DIN 52184).

Static bending tests for the determination of modulus of elasticity (MOE) and modulus of rupture (MOR) were performed with a Zwick-Roell Z020 testing machine (Software testXpert V10.11) according to DIN 52186 standards (three-point bending). Axial compression strength and Janka hardness in the axial and transverse directions were determined according to DIN 52185 and ASTM D143-94 standards, respectively.

Results and discussion

The results obtained on the physical and mechanical properties of *P. leucodermis* wood are shown in Table II together with available literature values for *P. leucodermis* and the two main commercial pine species in the region, namely Scots pine (*Pinus sylvestris*) and Austrian pine (*Pinus nigra*). It should be noted that it is unknown whether the literature values given by Tsoumis (1991) refer to heartwood or sapwood. Consequently, they allow only a relative comparison with the values obtained in this study. Except for Tsoumis (1991), no other reference could be located providing information on properties of *P. leucodermis* wood.

Pinus leucodermis wood was found to possess quite different physical and mechanical properties from those reported for *P. leucodermis*, Scots pine and Austrian pine. Density values (oven-dry 0.64 g cm⁻³, air-dry 0.73 g cm⁻³) were higher, while shrinkage (radial 1.9%, tangential 3.4%) was much lower (almost half) than the densities of

Table II. Physical and mechanical properties of *Pinus leucodermis* wood and literature values.

Property	<i>P. leucodermis</i> wood ^a	Literature values ^b		
		<i>P. leucodermis</i>	<i>P. sylvestris</i>	<i>P. nigra</i>
Wood density (g cm ⁻³)				
Oven-dry	0.64 ± 0.03	0.47	0.49	0.52
Air-dry	0.73 ± 0.04	0.53	0.53	0.55
Shrinkage (%)				
Radial	1.9 ± 0.4	4.1	4.0	4.1
Tangential	3.4 ± 0.6	6.0	7.7	7.7
Ratio T/R shrinkage	1.8 ± 0.2	1.5	1.9	1.9
Swelling (%)				
Radial	2.0 ± 0.5	–	–	–
Tangential	3.8 ± 0.7	–	–	–
MOE (N mm ⁻²)	7,087 ± 1,275	–	11,765	11,765
MOR (N mm ⁻²)	77 ± 6	69	98	103
Axial compression (N mm ⁻²)	41.6 ± 4.2	40	54	39
Hardness (Janka) (N mm ⁻²)				
Axial	48.0 ± 1.4	–	29	–
Transverse	33.4 ± 2.2	–	–	–

Note: ^amean ± SD; ^bdata from Tsoumis (1991).

MOE = modulus of elasticity; MOR = modulus of rupture.

0.47–0.55 g cm⁻³ and shrinkage values of 4.0–7.7% given by Tsoumis (1991). The large differences in density and shrinkage from the *P. leucodermis* literature values may be attributed to the origin of the material used in the study (heartwood) and its chemical composition (e.g. high content of extractives).

The average MOE was 7087 N mm⁻², which is very low compared with that of the other two pine species (11,765 N mm⁻²). MOR was 77 N mm⁻², which is also lower. The compression strength parallel to grain of *P. leucodermis* wood averaged 41.6 N mm⁻². This value is comparable to the reported axial compression for *P. leucodermis* and Austrian pine, but lower than that of Scots pine. It was observed that almost all specimens exhibited an overall compression failure of the “shearing type” according to ASTM D 143-83 standard. Finally, the Janka hardness found to be 33.4 N mm⁻² in the transverse direction and 48.0 N mm⁻² in the longitudinal direction.

Acknowledgements

No funding has been received for the research work. The authors wish to acknowledge the technical assistance of Mr. Ioannis Giannoulas of TEI Larissa.

References

- ASTM D 143-94 (2005). Standard methods of testing small clear specimens of timber. *The ASTM book of standards*. Philadelphia, PA: American Society for Testing and Materials.
- DIN 52184 (1979). *Prüfung von Holz; Bestimmung der Quellung und Schwindung*. DIN-Taschenbuch 31. Beuth, Germany: DIN.
- DIN 52185 (1976). *Prüfung von Holz; Bestimmung der Druckfestigkeit parallel zur Faser*. DIN-Taschenbuch 31. Beuth, Germany: DIN.
- DIN 52186 (1978). *Prüfung von Holz; Biegeversuch*. DIN-Taschenbuch 31. Beuth, Germany: DIN.
- Farjon, A. (2005). *Pines. Drawings and descriptions of the genus Pinus* (2nd ed.). Leiden: E. J. Brill and W. Backhuys.
- Tsoumis, G. (1991). *Science and technology of wood: Structure, properties, utilization*. New York: Van Nostrand Reinhold.